

ISSN 2518-170X (Online),
ISSN 2224-5278 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ
Қ. И. Сәтпаев атындағы Қазақ ұлттық техникалық зерттеу университеті

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН
Қазақстан Республикасының Ғылым Академиясының
Қ. И. Сәтпаев атындағы Қазақ ұлттық техникалық зерттеу университеті

NEWS

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN
Kazakh national research technical university
named after K. I. Satpayev

SERIES OF GEOLOGY AND TECHNICAL SCIENCES

6 (438)

NOVEMBER – DECEMBER 2019

THE JOURNAL WAS FOUNDED IN 1940

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

NAS RK is pleased to announce that News of NAS RK. Series of geology and technical sciences scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of geology and technical sciences in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of geology and engineering sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді геология және техникалық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия геологии и технических наук» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК. Серия геологии и технических наук в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по геологии и техническим наукам для нашего сообщества.

Б а с р е д а к т о р ы
э. ғ. д., профессор, ҚР ҰҒА академигі

И.К. Бейсембетов

Бас редакторының орынбасары

Жолтаев Г.Ж. проф., геол.-мин. ғ. докторы

Р е д а к ц и я а л қ а с ы:

Абаканов Т.Д. проф. (Қазақстан)
Абишева З.С. проф., академик (Қазақстан)
Агабеков В.Е. академик (Беларусь)
Алиев Т. проф., академик (Әзірбайжан)
Бакиров А.Б. проф., (Қырғыстан)
Беспәев Х.А. проф. (Қазақстан)
Бишимбаев В.К. проф., академик (Қазақстан)
Буктуков Н.С. проф., академик (Қазақстан)
Булат А.Ф. проф., академик (Украина)
Ганиев И.Н. проф., академик (Тәжікстан)
Грэвис Р.М. проф. (АҚШ)
Ерғалиев Г.К. проф., академик (Қазақстан)
Жуков Н.М. проф. (Қазақстан)
Қожахметов С.М. проф., академик (Қазақстан)
Конторович А.Э. проф., академик (Ресей)
Курскеев А.К. проф., академик (Қазақстан)
Курчавов А.М. проф., (Ресей)
Медеу А.Р. проф., академик (Қазақстан)
Мұхамеджанов М.А. проф., корр.-мүшесі (Қазақстан)
Нигматова С.А. проф. (Қазақстан)
Оздоев С.М. проф., академик (Қазақстан)
Постолатий В. проф., академик (Молдова)
Ракишев Б.Р. проф., академик (Қазақстан)
Сейтов Н.С. проф., корр.-мүшесі (Қазақстан)
Сейтмуратова Э.Ю. проф., корр.-мүшесі (Қазақстан)
Степанец В.Г. проф., (Германия)
Хамфери Дж.Д. проф. (АҚШ)
Штейнер М. проф. (Германия)

«ҚР ҰҒА Хабарлары. Геология мен техникалық ғылымдар сериясы».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» РҚБ (Алматы қ.).

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде 30.04.2010 ж. берілген №10892-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік.

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,
<http://www.geolog-technical.kz/index.php/en/>

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2019

Редакцияның Қазақстан, 050010, Алматы қ., Қабанбай батыра көш., 69а.

мекенжайы: Қ. И. Сәтбаев атындағы геология ғылымдар институты, 334 бөлме. Тел.: 291-59-38.

Типографияның мекенжайы: «Аруна» ЖК, Алматы қ., Муратбаева көш., 75.

Г л а в н ы й р е д а к т о р
д. э. н., профессор, академик НАН РК

И. К. Бейсембетов

Заместитель главного редактора

Жолтаев Г.Ж. проф., доктор геол.-мин. наук

Р е д а к ц и о н н а я к о л л е г и я:

Абаканов Т.Д. проф. (Казахстан)
Абишева З.С. проф., академик (Казахстан)
Агабеков В.Е. академик (Беларусь)
Алиев Т. проф., академик (Азербайджан)
Бакиров А.Б. проф., (Кыргызстан)
Беспаяев Х.А. проф. (Казахстан)
Бишимбаев В.К. проф., академик (Казахстан)
Буктуков Н.С. проф., академик (Казахстан)
Булат А.Ф. проф., академик (Украина)
Ганиев И.Н. проф., академик (Таджикистан)
Грэвис Р.М. проф. (США)
Ергалиев Г.К. проф., академик (Казахстан)
Жуков Н.М. проф. (Казахстан)
Кожаметов С.М. проф., академик (Казахстан)
Конторович А.Э. проф., академик (Россия)
Курскеев А.К. проф., академик (Казахстан)
Курчавов А.М. проф., (Россия)
Медеу А.Р. проф., академик (Казахстан)
Мухамеджанов М.А. проф., чл.-корр. (Казахстан)
Нигматова С.А. проф. (Казахстан)
Оздоев С.М. проф., академик (Казахстан)
Постолатий В. проф., академик (Молдова)
Ракишев Б.Р. проф., академик (Казахстан)
Сейтов Н.С. проф., чл.-корр. (Казахстан)
Сейтмуратова Э.Ю. проф., чл.-корр. (Казахстан)
Степанец В.Г. проф., (Германия)
Хамфери Дж.Д. проф. (США)
Штейнер М. проф. (Германия)

«Известия НАН РК. Серия геологии и технических наук».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10892-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел.: 272-13-19, 272-13-18,
<http://nauka-nanrk.kz/geology-technical.kz>

© Национальная академия наук Республики Казахстан, 2019

Адрес редакции: Казахстан, 050010, г. Алматы, ул. Кабанбай батыра, 69а.

Институт геологических наук им. К. И. Сатпаева, комната 334. Тел.: 291-59-38.

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

E d i t o r i n c h i e f

doctor of Economics, professor, academician of NAS RK

I. K. Beisembetov

Deputy editor in chief

Zholtayev G.Zh. prof., dr. geol-min. sc.

E d i t o r i a l b o a r d:

Abakanov T.D. prof. (Kazakhstan)
Abisheva Z.S. prof., academician (Kazakhstan)
Agabekov V.Ye. academician (Belarus)
Aliyev T. prof., academician (Azerbaijan)
Bakirov A.B. prof., (Kyrgyzstan)
Bespayev Kh.A. prof. (Kazakhstan)
Bishimbayev V.K. prof., academician (Kazakhstan)
Buktukov N.S. prof., academician (Kazakhstan)
Bulat A.F. prof., academician (Ukraine)
Ganiyev I.N. prof., academician (Tadjikistan)
Gravis R.M. prof. (USA)
Yergaliev G.K. prof., academician (Kazakhstan)
Zhukov N.M. prof. (Kazakhstan)
Kozhakhmetov S.M. prof., academician (Kazakhstan)
Kontorovich A.Ye. prof., academician (Russia)
Kurskeyev A.K. prof., academician (Kazakhstan)
Kurchavov A.M. prof., (Russia)
Medeu A.R. prof., academician (Kazakhstan)
Muhamedzhanov M.A. prof., corr. member. (Kazakhstan)
Nigmatova S.A. prof. (Kazakhstan)
Ozdoyev S.M. prof., academician (Kazakhstan)
Postolatii V. prof., academician (Moldova)
Rakishev B.R. prof., academician (Kazakhstan)
Seitov N.S. prof., corr. member. (Kazakhstan)
Seitmuratova Ye.U. prof., corr. member. (Kazakhstan)
Stepanets V.G. prof., (Germany)
Humphery G.D. prof. (USA)
Steiner M. prof. (Germany)

News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)

The certificate of registration of a periodic printed publication in the Committee of information and archives of the Ministry of culture and information of the Republic of Kazakhstan N 10892-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,
<http://nauka-nanrk.kz/geology-technical.kz>

© National Academy of Sciences of the Republic of Kazakhstan, 2019

Editorial address: Institute of Geological Sciences named after K.I. Satpayev
69a, Kabanbai batyr str., of. 334, Almaty, 050010, Kazakhstan, tel.: 291-59-38.

Address of printing house: ST "Aruna", 75, Muratbayev str, Almaty

NEWS**OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN
SERIES OF GEOLOGY AND TECHNICAL SCIENCES**

ISSN 2224-5278

Volume 6, Number 438 (2019), 295 – 301

<https://doi.org/10.32014/2019.2518-170X.181>

UDC 691.16:625.7/.8

M. Porto¹, P. Caputo¹, V. Loise¹, B. Teltayev², R. Angelico³, P. Calandra⁴, C. Oliviero Rossi¹¹Department of Chemistry and Chemical Technologies of University of Calabria,
Via P. Bucci, Cubo 14/D, 87036 Rende (CS) Italy,²Kazakhstan Highway Research Institute, Almaty, Kazakhstan,³Department of Agricultural, Environmental and Food Sciences (DIAAA), University of Molise,
Via De Sanctis, 86100 Campobasso (CB), Italy,⁴CNR-ISMN, National Council of Research, Via Salaria km 29.300, 00015 Monterotondo Stazione (RM), Italy.E-mail: michele.parto@unical.it, paolino.caputo@unical.it, valeria.loise@unical.it,
bagdatbt@yahoo.com, angelico@unimol.it, pietro.calandra@ismn.cnr.it, cesare.oliviero@unical.it**NEW EXPERIMENTAL APPROACHES TO ANALYSE
THE SUPRAMOLECULAR STRUCTURE
OF REJUVENATED AGED BITUMENS**

Abstract. Bitumen aging occurs through volatilization, oxidation and supramolecular assembly variations involving drastic changes in the structure of the material. Due to the ageing process of bitumen and its corresponding increase in viscosity, the stiffness of asphalt pavement is increased during its lifetime. Chemically, the relative content between asphaltenes and maltenes in the bitumen shifts towards a lower maltene fraction. Therefore, addition of high amounts of Reclaimed Asphalt Pavement (RAP) in asphalt mixtures may negatively affect the quality and performance of the final mix design. Rejuvenating agents can assist in this process by decreasing the aged bitumen's viscosity and restoring its original properties. An efficient rejuvenating agent favors their organization of the colloidal structure of the oxidized bitumen, thus recreating a supramolecular structure similar to fresh bitumen. Then, novel experimental approaches are needed to evaluate the efficiency of rejuvenators as well as the effect such additives have on aged bitumen properties. To achieve the aforementioned purpose, two advanced experimental approaches able to provide detailed information on bitumen microstructure are examined here. The essential concepts underlying the scattering and NMR techniques will be reviewed and the results of some recent applications of these methods in the evaluation of the effectiveness of the RAP rejuvenation will be synthetically illustrated.

Key words: rejuvenators, bitumen, aging, scattering, PXRD, NMR, relaxometry.

Introduction. Many important physical, mechanical, rheological and other characteristics of asphalt concretes depend considerably on bitumen properties [1-6]. But bituminous materials are easily subject to oxidative aging during pavement service life, especially in conditions of thermal and / or ultraviolet radiation [7, 8]. It is well assessed that oxidized bitumen is characterized by reprocessing temperatures higher than fresh one, because most of the condensed aromatic components and resins, which are responsible for a certain grade of mobility, are converted into highly oxygenated polar and more saturated compounds (asphaltenes and saturates), [9]. Indeed, the depletion of polycyclic aromatic compounds with amphiphilic activity and acting as supramolecular cage surrounding the polar asphaltenes, may lead to an increase of average colloidal sizes dispersed in the continuous a polar maltene phase. This phenomenon in turn gives rise to loss of elasticity and predisposition to material failure. Thus, once removed and processed, the bituminous layers can be recycled as reclaimed asphalt pavements (RAPs), even though their reuse is still limited (less than 20% in the mix design) due to their poor bulk mechanical properties (complex modulus and viscosity), which can cause premature cracking failures. The RAP performances as asphalt binders may be partially restored towards their original state upon addition of several classes of compounds called rejuvenators [10-12]. In particular, at least two classes of rejuvenators can be

distinguished on the basis of the mechanism by which they exert their respective regenerating action, namely, softening agents (usually called flux oils, lube stock, slurry oils etc.) able to decrease the viscosity of the aged binder, and real rejuvenators capable to restore the physicochemical properties of bitumen whose virgin microstructure has been altered by volatilization and oxidative processes [13]. To the former type belong the rheological rejuvenators (commonly taken from vegetable oil wastes), which should replenish the volatiles and light chemical fractions that have been lost during aging of asphalts, and rebalance the asphaltene/maltene ratio typical of fresh bitumen. The latter category comprises novel rejuvenators related to the general class of surfactants. Indeed, thanks to its capability to lower the interfacial energy between two immiscible phases, an amphiphilic molecule can bind on a side the polar phase and on the other side the a polar one, due to the simultaneous presence within its molecular architecture of both polar and non-polar moieties. The overall result of these simultaneous interactions proved to be effective in the stabilization of clusters of polar molecules dispersed in polar solvents [14, 15].

Therefore, amphiphilic molecules are expected to work similarly well in improving the dispersion of asphaltene clusters in the maltene phase, and consequently counteracting the aging process and reverting to rejuvenation eventually [16, 17].

The efficient and targeted use of additives with documented rejuvenating action on RAPs employed in the road paving industry must be based primarily on a rigorous experimental investigation of their effect exerted on the colloidal microstructure of bitumen. However, although these additives play an important role in bitumen recycling methods, their impact on the bitumen supramolecular structure arrangement has not yet been fully investigated in depth. The purpose of the present contribution is to emphasize the potentialities of advanced experimental methods such as scattering techniques and nuclear magnetic relaxometry, which can be considered promising techniques in the elucidation of the dynamics of the complex microstructure in bitumen. In fact, unlike the results acquired through the analysis of the mechanical bulk properties, scattering (in particular X-ray scattering) and NMR experiments can probe from nano- to mesoscale level the effectiveness of a rejuvenator in restoring the microstructure of bitumen subjected to the drastic action of aging processes [18, 19]. This work underlines that the detailed analysis of the microstructural dynamics of bitumen, extending the information taken from commonly used empirical and rapid methods, allows us to better understand the phenomena that occur in such complex materials, providing new tools for the piloted design of ever-performing rejuvenations.

Experimental methods. Information on how rejuvenators can affect the supramolecular structure and distribution of aggregates within the bituminous colloidal network and how this may affect the overall material properties can be achieved from careful analyses of Powder X-Ray Diffraction (PXRD) data and NMR measurements performed at low magnetic fields (^1H -NMR Relaxometry), making these techniques very powerful methods to carry out structural investigation in such complex systems [18, 20].

Application of X-ray scattering techniques for the analysis of bitumen. X-ray scattering techniques represent non-destructive analytical methods able to reveal information about the crystallographic structure, chemical composition, and physical properties of materials and thin films. These techniques are based on observing the scattered intensity of an X-ray beam hitting a sample as a function of incident and scattered angle, polarization, and wavelength or energy [21]. The PXRD spectrum provides the nano-structural information as well as the crystallite parameter of the molecules that are associated with the asphaltene aggregates [22-24]. For structure investigations on length scales longer than a few nm, Small-Angle X-ray Scattering (SAXS) is best suitable, whereas in the wide angle range (WAXS) the spectrum furnishes precious indications about characteristic distances belonging to various atomic and molecular organizations of different levels of complexity.

Application of Nuclear Magnetic Resonance techniques for the analysis of bitumen. Nuclear Magnetic Resonance (NMR) spectroscopy has been recently found to be an efficient and powerful technique for the characterization of complex materials such as bitumen [25]. One of the advantages of this technique is the ability to simultaneously identify several components of the mixture with the acquisition of a single high resolution ^1H -NMR spectrum and, consequently, to evaluate the relative amount of the aliphatic and aromatic hydrogens portion in the complex system. In particular, dynamics information can be obtained from ^1H spin-spin relaxation time (T_2) measurements according to the Carr-Purcell-Meiboom-Gill (CPMG) pulse sequence (NMR Relaxometry) [26, 27]. Usually the T_2 varies all over the sample because

of the sample heterogeneity or surface relaxation differences; then a multi-exponential attenuation of the NMR spin echo envelope should be observed. The relaxation time probability distribution function can be obtained by applying an inverse Laplace transform (ILT) to the experimental data [28]. The T_2 relaxation time distribution can be considered a structural fingerprint of the bitumen in which the changes in relaxation times reflect the changes that occur in the structure of the colloidal binder. In general, by ILT NMR relaxometry one can monitor the structural evolution of bitumen when additives (polymers, surfactants and so on) are added, since the relaxation distribution is strongly affected by the supramolecular organisation present in the colloids. In particular, the powerful ILT method applied to the experimental NMR echo decay can be exploited to test the effectiveness of the real rejuvenator. Indeed, direct correlation can be made between T_2 and the rigidity of structures in these materials as well as the molecular constrain causing dynamic hindrance [29].

Results and discussion. The bulk mechanical properties of bituminous materials such as, e.g., ductility and rigidity, are empirically determined by the amplitude oscillatory rheometry through the measurement of the complex modulus G^* consisting in its real (elastic modulus G') and imaginary (viscous modulus G'') components [30-33]. However, more sophisticated experimental investigations such as NMR relaxometry and X-ray scattering are being proposed as emerging methods for the comprehension of the microscopic/molecular processes underneath the observed behaviour of a bituminous material subjected to both physical and chemical treatments. Indeed, the application of low-field NMR spectroscopy has been used for the determination of physical properties of petroleum fractions [25, 29] and the Inverse Laplace Transform analysis of the NMR echo signal decay gives the transverse (or spin-spin) relaxation time T_2 that can be connected to different domains characterized by different rigidities [20]. The chemical reasoning for this lies on the molecular constrain causing dynamic hindrance and lowering T_2 , an effect that can be considered quite general and already found also in different systems [34-36]. In bitumen, the T_2 relaxation time distribution profile is usually characterized by two distinct peaks.

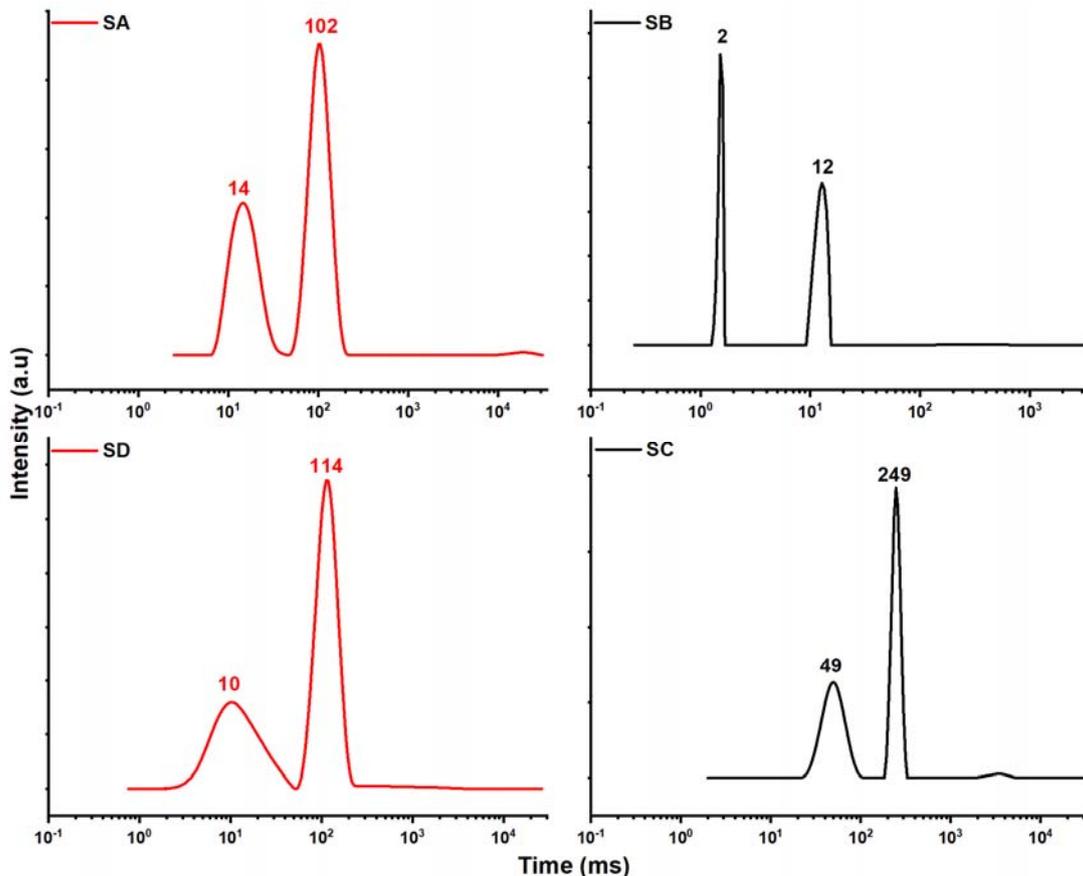


Figure 1 - T_2 relaxation time distribution functions obtained for pristine bitumen (SA) at 50°C, PAV bitumen (SB) at 70°C, PAV bitumen + 2 wt% vegetable flux oil (SC) at 60°C and PAV bitumen + 2 wt% green rejuvenator (SD) at 60 °C

The short T_2 times (around 10 ms) arise from slow tumbling of more rigid supra-molecular aggregates; hence they can be reasonably attributed to the dynamics of asphaltenes. Conversely, long T_2 times (around 100 ms) connected to low intra-molecular interactions can be referred to the maltene fraction of the sample under examination. The T_2 profiles illustrated in figure 1 provide an example of the application of the ILT method in the choice of the right rejuvenator through a quick comparison of the T_2 distributions for different treatments subjected to the same bituminous matrix. Indeed, one can easily verify that the addition of a green rejuvenator to the oxidized bitumen (PAV bitumen), has the effect of restoring the original probability density function compatible with fresh pristine bitumen (compare SA with SD). On the other hands, the pattern is only partially recovered when a flux oil (a softening agent) is used (compare SA with SC).

Structural features of the asphaltene clusters self-aggregated in the maltene phase can be also investigated by the X-ray scattering technique in order to gain new results on the role played by some additives in the rejuvenation action of bitumen whose colloidal structure has been seriously compromised by the aging processes. Indeed, the eventual presence of an additive triggers the formation of further intermolecular interaction in competition with those responsible for this self-assembly, causing a change of the size and shape of these aggregates. A representative X-Ray scattering spectrum of bitumen together with the Lorentzian deconvolution reported in figure 2 as a function of scattering vector $q = 4\pi \sin \theta / \lambda$, illustrates several important features.

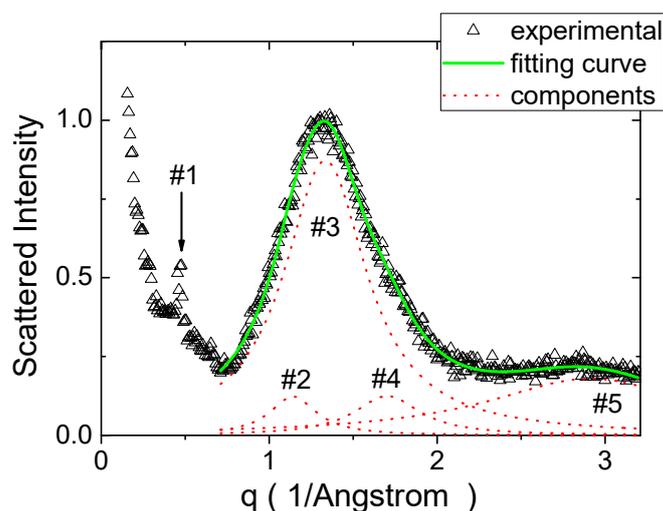


Figure 2 – Typical Wide Angle X-Ray diffraction pattern of asphalt binder with peak profile analysis

The most prominent band centred at around 1.3 \AA^{-1} gives a characteristic of $4.4\text{-}4.7 \text{ \AA}$, which can be attributed to the typical intermolecular lateral distance commonly present in disordered fluids. This length parameter results to be slightly higher than that identified from the band of graphene (lateral distance of about 3.6 \AA) and coming from the stacks in the aromatic compounds. However, owing to the coexistence of aliphatic components in the bitumen it is reasonable to treat this band as an unresolved superposition of these two contributions. Therefore, deconvolution procedures in terms of bell-shaped curves are necessary to discriminate all the signals. Besides, an eventual low-intensity reflection in the range $0.3\text{-}0.8 \text{ \AA}^{-1}$ can be attributed to the occurrence of a supra-molecular aggregation and would be therefore associated to a repetition distance between one asphaltene local aggregate and its neighbouring one, in accordance with a model of a complex system with different levels of complexity. Finally, for $q < 0.3 \text{ \AA}^{-1}$ the fractal aggregation generated by an ensemble of asphaltene clusters can be examined. In principle, the formation of self-similar, fractal structures in bituminous materials cannot be excluded. In such case, the interfacial boundary is not sharp and a scaling law between the mass M (or particle number N) and the enclosed volume is established, which can provide an indication of how efficiently the particles are packed. The presence of additives may modify not only the fractal structure but also the intermolecular assembly as probed by the band centred at 1.3 \AA^{-1} and the peak around 0.5 \AA^{-1} .

Conclusion. The restoring of the aged bitumen structure to the original conditions is a challenging task due to its complex organization at the supra-molecular scale. It has been emphasized that scattering techniques and nuclear magnetic relaxometry represent promising methods of investigation that deserve attention for a deeper analysis of bituminous materials. In fact, they can probe the effectiveness of a rejuvenator in restoring the bitumen microstructure after the aging process, while the mechanical properties alone do not allow reaching this degree of microstructural knowledge. In conclusion, we want to bring to the attention the fact that the detailed analysis of the physics of molecular bitumens allows us to better understand the phenomena that occur in bitumen, providing new tools for the piloted design of new rejuvenators with ad-hoc performances.

М. Порто¹, П. Капуто¹, В. Лоиз¹, Б. Телтаев², Р. Агенлико³, П. Каландра⁴, Ч. Оливиеро Росси¹

¹Калабрия Университеті Химия және Химия Технологиялары кафедрасы, Италия,

²Қазақстан Жол Ғылыми-Зерттеу институты, Алматы, Қазақстан,

³Ауыл шаруашылығы, Экология және Тағам Ғылымдары кафедрасы (DIAAA), Молиз Университеті, Италия,

⁴CNR-ISMN, Ұлттық Ғылыми Зерттеулер Кеңесі, Италия

ЖАСАРТЫЛҒАН ЕСКІРГЕН БИТУМДАРДЫҢ МОЛЕКУЛАЛЫҚ ҚҰРЫЛЫМЫН ТАЛДАУҒА АРНАЛҒАН ЖАҢА ТӘЖІРИБЕЛІК ТӘСІЛДЕР

Аннотация. Битумның ескіруі материал құрылымындағы өзгерістермен байланысты болатын булану, тотығу және молекулалық қосылыстардағы өзгерістердің нәтижесінде орын алады. Битумның ескіру үдерісіне және оның тұтқырлығының артуына байланысты асфальтбетон жамылғысының қаттылығы пайдалану кезінде арта түседі. Химиялық тұрғыдан түсіндіргенде, битумдағы асфальтендер пен мальтендердің салыстырмалы үлесі мальтендердің төмен құрамына қарай жылжиды. Сондықтан, қайта қалпына келтірілген асфальт жамылғысын (ҚАЖ) асфальт қоспаларына көп мөлшерде қосу асфальтбетон жамылғысының сипаттамасына теріс әсер етуі мүмкін. Жасартқыш реагенттер ескірген битумның тұтқырлығын азайту және оның бастапқы қасиеттерін қалпына келтіруі арқылы осы үдерісті жақсартуы мүмкін. Тиімді жасартқыш реагент тотыққан битумның коллоидті құрылымының ұйымдасуына қолайлы жағдай туғызып, жаңадан дайындалған битумның молекулалы құрылымын қалпына келтіреді. Одан басқа, жаңа тәжірибелік тәсілдер жасартқыш реагенттердің тиімділігі мен мұндай қоспалардың ескірген битумның қасиеттеріне ықпалын бағалау үшін қажет. Жоғарыда аталған мақсаттарға қол жеткізу үшін, осы мақалада битумның микроқұрылымы туралы толық ақпарат беретін неғұрлым перспективалық тәсілдер қарастырылады. Сейілу және ЯМР әдістерінің негізі болған басты тұжырымдамалар қарастырылады, сондай-ақ ҚАЖ жасартудың тиімділігін бағалауда осы әдістерді синтетикалық пайдалану нәтижелері көрсетілді.

Түйін сөздер: жасартқыш реагенттер, битум, ескіру, сейілу, рентген дифракциясы (ҰРД), ядролық-магниттік резонанс (ЯМР), релаксометрия.

М. Порто¹, П. Капуто¹, В. Лоиз¹, Б. Телтаев², Р. Агенлико³, П. Каландра⁴, Ч. Оливиеро Росси¹

¹Кафедра Химии и химических технологий университета Калабрии, Италия,

²Казахстанский дорожный научно-исследовательский институт, Алматы, Казахстан,

³Кафедра Сельскохозяйственных, экологических и пищевых наук (DIAAA), Университет Молиз, Италия,

⁴CNR-ISMN, Национальный совет научных исследований, Италия

НОВЫЕ ЭКСПЕРИМЕНТАЛЬНЫЕ ПОДХОДЫ К АНАЛИЗУ НАДМОЛЕКУЛЯРНОЙ СТРУКТУРЫ ОМОЛОЖЕННЫХ СОСТАРЕННЫХ БИТУМОВ

Аннотация. Старение битума происходит из-за выпаривания, окисления и изменений в надмолекулярных соединениях, связанных со значительными изменениями в структуре материала. В связи с процессом старения битума и соответствующего увеличения его вязкости, жесткость асфальтобетонного покрытия увеличивается во время эксплуатации. В химическом смысле относительное содержание между асфальтенами и мальтенами в битуме сдвигается в сторону более низкого содержания мальтенов. Поэтому добавление большого количества регенерированного асфальтового покрытия (РАП) в асфальтовые смеси может отрицательно повлиять на качество и характеристики окончательного состава смеси. Омолаживающие реагенты

могут способствовать улучшению данного процесса путем уменьшения вязкости состаренного битума и восстановления его первоначальных свойств. Эффективный омолаживающий реагент благоприятствует организации коллоидной структуры окисленного битума, тем самым восстанавливая надмолекулярную структуру свежеприготовленного битума. Затем, новые экспериментальные подходы необходимы для оценки эффективности омолаживающих реагентов, а также какое влияние оказывают такие добавки на свойства состаренного битума. Чтобы достичь вышеуказанной цели, в данной статье рассматриваются два наиболее перспективных подхода, способные предоставить подробную информацию о микроструктуре битума. Будут рассмотрены основополагающие концепции, лежащие в основе методик рассеивания и ЯМР, а также будут проиллюстрированы результаты некоторых недавних синтетических применений этих методов в оценке эффективности омолаживания РАП.

Ключевые слова: омолаживающие реагенты, битум, старение, рассеивание, рентгеновская дифракция (ПРД), ядерно-магнитный резонанс (ЯМР), релаксометрия.

Information about authors:

Porto Michele, PhD Student “Life Science”, Department of Chemistry and Chemical Technologies of University of Calabria, Italy; michele.parto@unical.it; <https://orcid.org/0000-0001-6019-1089>

Caputo Paolino, Research fellow Department of Chemistry and Chemical Technologies of University of Calabria, Italy; paolino.caputo@unical.it; <https://orcid.org/0000-0003-3472-7710>

Loise Valeria, PhD Student “Life Science”, Department of Chemistry and Chemical Technologies of University of Calabria, Italy; valeria.loise@unical.it; <https://orcid.org/0000-0001-5156-5077>

Teltayev Bagdat Burkhanbaiuly, Doctor of Technical Sciences, President of JSC “Kazakhstan Highway Research Institute”, Almaty, Kazakhstan; bagdatbt@yahoo.com; <https://orcid.org/0000-0002-8463-9965>

Angelico Ruggero, PhD, Senior researcher in chemistry and physics of soft and hard matter, Department of Agricultural, Environmental and Food Sciences (DIAAA), University of Molise, Campobasso (CB), Italy; angelico@unimol.it; <https://orcid.org/0000-0002-0769-5680>

Calandra Pietro, Researcher CNR-ISMN, National Council of Research, Monterotondo Stazione (RM), Italy; pietro.calandra@ismn.cnr.it; <https://orcid.org/0000-0002-4479-4311>

Oliviero Rossi Cesare, Professor of physical chemistry, President of the spin-off “Kimical” at University of Calabria, Department of Chemistry and Chemical Technologies of University of Calabria, Italy; cesare.oliviero@unical.it; <https://orcid.org/0000-0003-4406-7824>

REFERENCES

[1] Iskakbayev A.I., Teltayev B.B., Rossi C.O. Deformation and strength of asphalt concrete under static and step loadings // *Transport Infrastructure and Systems – Proceedings of the AIIT International Congress on Transport Infrastructure and Systems, TIS. 2017. P. 3-8 (in Eng.)*.

[2] Teltayev B.B., Amirbayev Y.D. Experimental evaluation of strength for asphalt and polymer modified asphalt concretes at low temperatures // *News of the National academy of sciences of the Republic of Kazakhstan. Series of Geology and Technical Sciences. 2017. 1 (421). P. 167-176 (in Eng.)*.

[3] Iskakbayev A.I., Teltayev B.B., Rossi C.O. Steady-state creep of asphalt concrete // *Applied Sciences. 2017. 7(2) 142 (in Eng.)*.

[4] Iskakbayev A.I., Teltayev B.B., Rossi C.O., Yensebayeva G.M. Experimental investigation of an asphalt concrete deformation under cyclic loading // *News of the National academy of sciences of the Republic of Kazakhstan. Series of Geology and Technical Sciences. 2018. 2 (428). P. 104-111 (in Eng.)*.

[5] Iskakbayev A.I., Teltayev B.B., Rossi C.O., Estayev K. A new simple damage accumulation model for predicting of an asphalt concrete cyclic strength // *News of the National academy of sciences of the Republic of Kazakhstan. Series of Geology and Technical Sciences. 2018. 5 (431). P. 38-47. doi.org/10.32014/2018.2518-170X.8 (in Eng.)*.

[6] Iskakbayev A.I., Teltayev B.B., Yensebayeva G.M., Kutimov K.S. Computer modelling of creep for hereditary materials by Abel’s kernel // *News of the National academy of sciences of the Republic of Kazakhstan. Series of Geology and Technical Sciences. 2018. 6(432). P. 66-76. doi.org/10.32014/2018.2518-170X.36 (in Eng.)*.

[7] Oliviero Rossi C., Caputo B., Baldino N., Szerb E.I., Teltayev B. Quantitative evaluation of organosilane-based adhesion promoter effect on bitumen-aggregate bond by contact angle test // *International Journal of Adhesion and Adhesives. 1 January 2017. Vol. 72. P. 117-122 (in Eng.)*.

[8] Oliviero Rossi C., Caputo P., Ashimova S., Fabozzi A., D’Errico G., Angelico R. Effects of natural antioxidant agents on the bitumen aging process: an EPR and rheological investigation // *Appl. Sci. 2018. N 8. P. 1405-1418 (in Eng.)*.

[9] Handle F., Harir M., Füssl J., Koyun A.N., Grossegger D., Hertkorn N., Eberhardsteiner L., Hofko B., Hospodka M., Blab R., Schmitt-Kopplin P., Grothe H. Tracking aging of bitumen and its saturate, aromatic, resin, and asphaltene fractions using high-field Fourier transform ion cyclotron resonance mass spectrometry // *Energy Fuels. 2017. N 31. P. 4771-4779 (in Eng.)*.

- [10] Zaumanis M., Mallick R.B., Poulidakos L., Frank R. Influence of six rejuvenators on the performance properties of Reclaimed Asphalt Pavement (RAP) binder and 100% recycled asphalt mixtures // *Constr. Build. Mater.* 2014. N 71. P. 538-550 (in Eng.).
- [11] Ashouri Taziani E., Toraldo E., Crispino M., Giustozzi F. Application of rejuvenators and virgin bitumen to restore physical and rheological properties of RAP binder // *Aust. J. Civil Eng.* 2017. N 15. P. 73-79 (in Eng.).
- [12] Oliviero Rossi C., Caputo P., Loise V., Ashimova S., Teltayev B., Sangiorgi C. A new green rejuvenator: Evaluation of structural changes of aged and recycled bitumens by means of rheology and NMR // In: Poulidakos L., Cannone Falchetto A., Wistuba M., Hofko B., Porot L., Di Benedetto H. (Eds) RILEM 252-CMB Symposium. 2018. RILEM Book Series. Vol. 20. Springer, Cham. (in Eng.).
- [13] Roberts F.L., Kandhal P.S., Brown E.R., Lee D.Y., Kennedy T.W. *Hot Mix Asphalt Materials, Mixture Design and Construction* / 2nd ed. NAPA, Lanham, MD. 1996. 576 p. (in Eng.).
- [14] Calandra P., Longo A., Ruggirello A., Turco Liveri V. Physico-Chemical Investigation of the State of Cyanamide Confined in AOT and Lecithin Reversed Micelles // *Journal of Physical Chemistry B.* 2004. 108, 8260-8268. DOI: 10.1021/jp0492422 (in Eng.).
- [15] Calandra P., Giordano C., Ruggirello A., Turco Liveri V. Physicochemical investigation of acrylamide solubilization in sodium bis (2-ethylhexyl) sulfosuccinate and lecithin reversed micelles // *Journal of Colloid and Interface Science.* 2004. 277, 206-214 DOI: 10.1016/j.jcis.2004.04.021 (in Eng.).
- [16] Kakar M.R., Hamzah M.O., Akhtar M.N. Surface free energy and moisture susceptibility evaluation of asphalt binders modified with surfactant-based chemical additive // *J. of Cleaner Prod.* 2016. N 112. P. 2342-2353 (in Eng.).
- [17] Caputo P., Porto M., Calandra P., De Santo M.P., Oliviero Rossi C. Effect of epoxidized soybean oil on mechanical properties of bitumen and aged bitumen // *Mol. Cryst. Liq. Cryst.* 2018. N 675. P. 68-74 (in Eng.).
- [18] Loise V., Caputo P., Porto M., Calandra P., Angelico R., Oliviero Rossi C. A review on bitumen rejuvenation: mechanisms, materials, methods and perspectives // *Appl. Sci.* 2019. N 9. P. 4316-4359 (in Eng.).
- [19] Szerb E.I., Nicotera I., Teltayev B., Vaiana R., Rossi C.O. Highly stable surfactant-crumb rubber-modified bitumen: NMR and rheological investigation // *Road Materials and Pavement Design.* 4 July 2018. Vol. 19, Issue 5. P. 1192-1202 (in Eng.).
- [20] Caputo P., Loise V., Crispini A., Sangiorgi C., Scarpelli F., Oliviero Rossi C. The efficiency of bitumen rejuvenator investigated through Powder X-ray Diffraction (PXRD) analysis and T₂-NMR spectroscopy // *Colloid Surface A.* 2019. N 571. P. 50-54 (in Eng.).
- [21] Zemb T., Lindner P. *Neutron, X-rays and Light Scattering Methods Applied to Soft Condensed Matter*, 1st edition, North Holland, Amsterdam, Netherlands. 2002. 552 p. (in Eng.).
- [22] Trejo F., Ancheyta J., Morgan T.J., Herod A.A., Kandiyoti R. Characterization of Asphaltene from Hydrotreated Products by SEC, LDMS, LAMDI, NMR, and XRD // *Energy Fuels.* 2007. N 21. P. 2121-2128 (in Eng.).
- [23] Calandra P., Caputo P., De Santo M.P., Todaro L., Turco Liveri V., Oliviero Rossi C. Effect of additives on the structural organization of asphaltene aggregates in bitumen // *Constr. Build. Mater.* 2019. N 199. P. 288-297 (in Eng.).
- [24] Tanaka R., Sato E., Hunt J.E., Winans R.E., Sato S., Takanohashi T. Characterization of Asphaltene Aggregates Using X-ray Diffraction and Small-Angle X-ray Scattering // *Energy Fuels.* 2004. N 18. P. 1118-1125 (in Eng.).
- [25] Oliviero Rossi C., Caputo P., De Luca G., Maiuolo L., Eskandarsefat S., Sangiorgi C. ¹H-NMR spectroscopy: a possible approach to advanced bitumen characterization for industrial and paving applications // *Appl. Sci.* 2018. N 8. P. 229-242 (in Eng.).
- [26] Angelico R., Ceglie A., Olsson U., Palazzo G., Ambrosone L. Anomalous surfactant diffusion in a living polymer system // *Physical Review E.* 2006. N 74. P. 031403-031410 (in Eng.).
- [27] Angelico R., Murgia S., Palazzo G. Reverse wormlike micelles: a special focus on Nuclear Magnetic Resonance investigations // *RSC Soft Matter.* 2017. N 6. P. 31-62 (in Eng.).
- [28] Caputo P., Loise V., Ashimova S., Teltayev B., Vaiana R., Oliviero Rossi C. Inverse Laplace Transform (ILT) NMR: A powerful tool to differentiate a real rejuvenator and a softener of aged bitumen // *Colloid Surface A.* 2019. N 574. P. 154-161 (in Eng.).
- [29] Barbosa L.L., Kock F.V.C., Silva R.C., Freitas J.C.C., Lacerda Jr V., Castro E.V.R. Application of low-field NMR for the determination of physical properties of petroleum fractions // *Energy Fuels.* 2013. N 27. P. 673-679 (in Eng.).
- [30] Filippelli L., Gentile L., Oliviero Rossi C., Ranieri G.A., Antunes F.E. Structural Change of Bitumen in the Recycling Process by Using Rheology and NMR // *Ind. Eng. Chem. Res.* 2012. N 51. P. 16346-16353 (in Eng.).
- [31] Yu X., Zaumanis M., dos Santos S., Poulidakos L.D. Rheological, microscopic, and chemical characterization of the rejuvenating effect on asphalt binders // *Fuel.* 2014. N 135. P. 162-171 (in Eng.).
- [32] Oliviero Rossi C., Caputo P., Loise V., Miriello D., Teltayev B., Angelico R. Role of a food grade additive in the high temperature performance of modified bitumens // *Colloid Surface A.* 2017. N 532. P. 618-624 (in Eng.).
- [33] Oliviero Rossi C., Ashimova S., Calandra P., De Santo M.P., Angelico R. Mechanical resilience of modified bitumen at different cooling rates: A rheological and atomic force microscopy investigation // *Appl. Sci.* 2017. N 7. P. 779-789 (in Eng.).
- [34] Olsson U., Börjesson J., Angelico R., Ceglie A., Palazzo G. Slow dynamics of wormlike micelles // *Soft Matter.* 2010. N 6. P. 1769-1777 (in Eng.).
- [35] Angelico R., Gentile L., Ranieri G. A., Oliviero Rossi C. Flow induced structures observed in a viscoelastic reverse wormlike micellar system by Magnetic Resonance Imaging and NMR velocimetry // *RSC Advances.* 2016. N 6. P. 33339-33347 (in Eng.).
- [36] Osman K.S., Taylor S.E. Insight into Liquid Interactions with Fibrous Absorbent Filter Media Using Low-Field NMR Relaxometry. Prospective Application to Water/Jet Fuel Filter-Coalescence // *Ind. Eng. Chem. Res.* 2017. N 56. P. 14651-14661 (in Eng.).

**Publication Ethics and Publication Malpractice
in the journals of the National Academy of Sciences of the Republic of Kazakhstan**

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайте:

[www:nauka-nanrk.kz](http://www.nauka-nanrk.kz)

ISSN 2518-170X (Online), ISSN 2224-5278 (Print)

<http://www.geolog-technical.kz/index.php/en/>

Верстка Д. Н. Калкабековой

Подписано в печать 15.11.2019.
Формат 70x881/8. Бумага офсетная. Печать – ризограф.
19,7 п.л. Тираж 300. Заказ 6.